


Laser Processing of 3M™ Thermally Conductive Adhesive Transfer Tape 8810

- Smooth laser-processed edges and minimal heat-affected zones
- No degradation to the physical properties of the materials
- Eliminates material deformation during processing
- Consistently and repeatedly process 3M tape 8810 to a high degree of dimensional accuracy

PROCESSING EXAMPLE

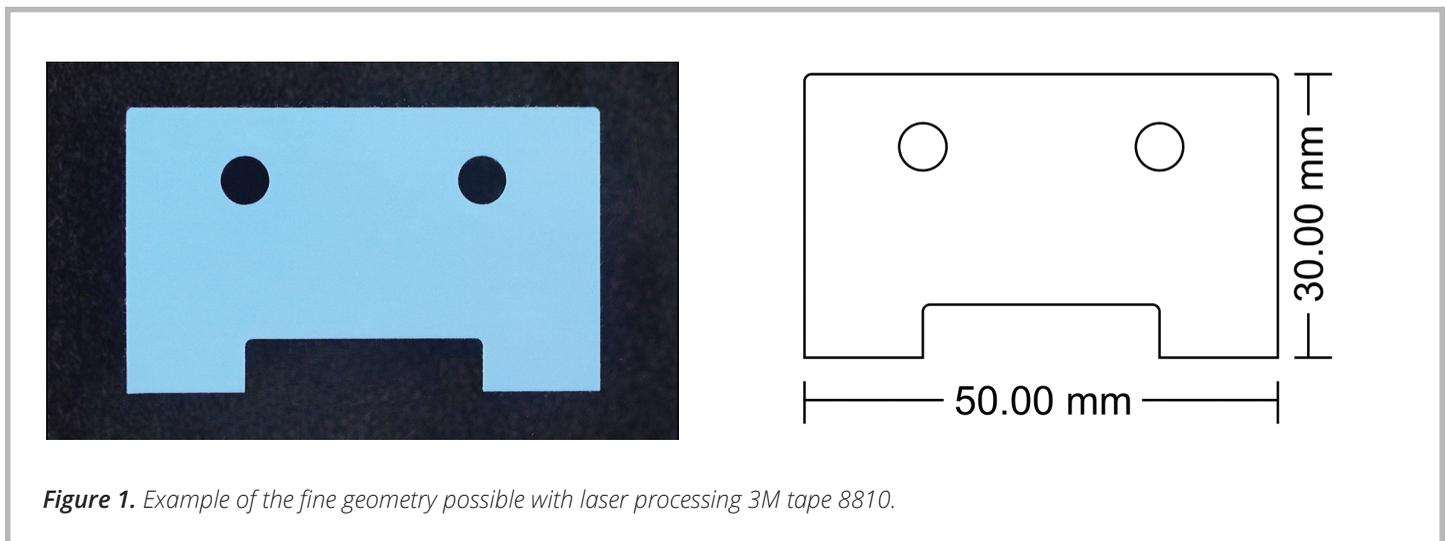

3M™ Thermally Conductive Adhesive Transfer Tape 8810 applications requiring fine geometry and intricate detail without degrading the physical properties of the material can be achieved with Universal Laser Systems technology. An example demonstrating the results of laser processing the 3M tape 8810 material is shown in *Figure 1*.

MATERIAL OVERVIEW

3M™ Thermally Conductive Adhesive Transfer Tape 8810 is designed to provide a preferential heat-transfer path between heat-generating components and heat sinks or other cooling devices (e.g., fans, heat spreaders, or heat pipes). The specialized chemistry of this tape renders them modestly soft and able to wet to many surfaces, allowing them to conform well to non-flat substrates, provide high adhesion, and act as a good thermal interface. The acrylate adhesive layer is available in a thickness of 0.25mm and is protected with PET release liners on both the top and bottom surfaces. A diagram depicting the layers of the 8810 material is shown in *Figure 2*.

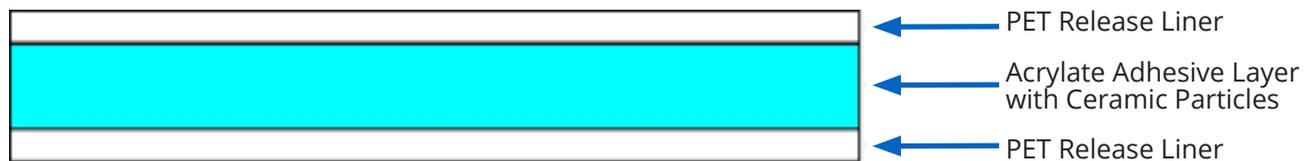


Figure 2. 3M tape 8810 diagram showing PET liners located on top and bottom of the acrylate adhesive layer with ceramic particles. The PET liners measure .05mm thick and the acrylate adhesive layer measures 0.25mm thick.

The delicate nature of 3M™ Thermally Conductive Adhesive Transfer Tapes makes them difficult to process with possible deformation when processed with traditional mechanical methods. The non-contact nature of laser processing overcomes this difficulty, which enables the processing of applications with fine geometry and intricate detail. Universal Laser Systems makes it simple to consistently and repeatedly process these materials.

LASER PROCESSING NOTES

3M tape 8810 was tested to assess laser processing compatibility and determine the best system configuration of laser peak power and wavelength. The PET liners absorb 9.3µm energy more efficiently than other wavelengths, meaning less peak power was necessary to produce good results with minimum heat effects. The acrylate adhesive layer also absorbs the 9.3µm wavelength efficiently with nominal heat effects along the processed path. Microscopy images taken at 200X magnification of the processed edge of the 3M tape 8810 post-processing with the liners in place and the liners removed are shown in **Figures 3** and **4**, respectively. In these images, it is shown that the PET liners contain most of the heat effects and discoloration, while the acrylate adhesive layer layer itself is relatively free of heat effects and discoloration. Further inspection of the laser-processed material shows that the acrylate adhesive layer is cleanly processed along the processed path with the 30 watt 9.3µm CO2 laser source.

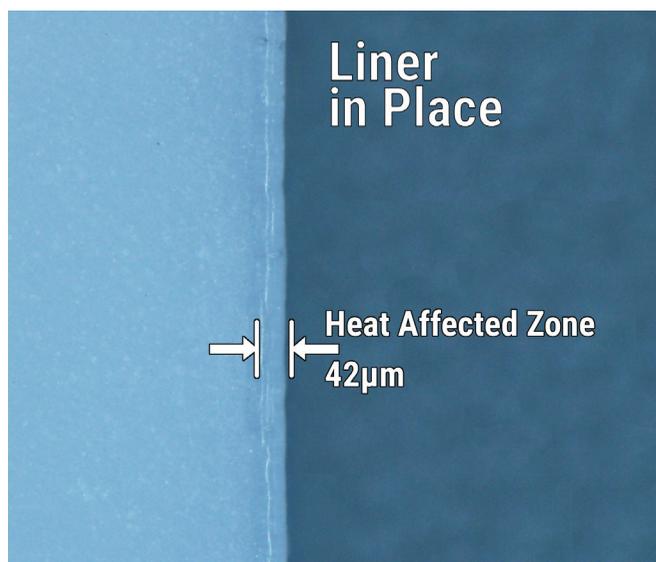


Figure 3. Microscopy image (200X) of the laser-processed edge of 3M tape 8810 with the PET liners in place. The heat-affected zone measures 42µm.

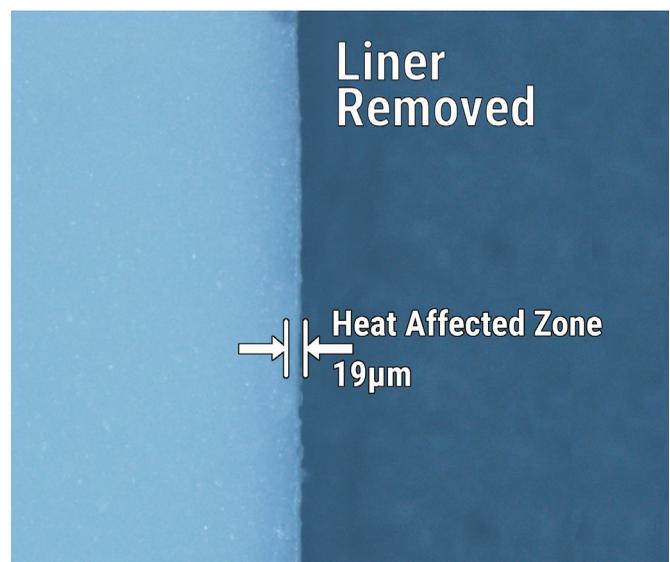



Figure 4. Microscopy image (200X) of the laser-processed edge of 3M tape 8810 with the PET liners removed from the material post-processing. The heat-affected zone measures 19µm.

ALTERNATIVE SYSTEM CONFIGURATION ANALYSIS

3M tape 8810 was also tested with an alternate system configuration of 10.6 μm laser energy at an equivalent laser power level for comparison and determination of the effectiveness of each system configuration. The results of these tests were compared by analyzing the heat effects, quality of the processed edge, and post-processing requirements. The results of the comparison of these system configurations are listed in tabular form in **Table 1** and shown photographically in **Figure 5**. Both system configurations appear viable with some reduction in quality of the results for the 10.6 μm configuration as stated in the comparison.

Table 1. System Configuration Comparison

System Configuration	Heat-Affected Zone	Process Characteristics	Post-Processing Requirements
9.3 μm (strongly recommended)	Minimal heat-affected zone of approximately 42 μm .	The 9.3 μm laser energy has the advantage of better absorption by the material resulting in a consistent edge along the processed path with a reduced heat-affected zone.	Processing of the 3M pad 8810 material with either the 9.3 μm or the 10.6 μm configuration did not require additional post-processing.
10.6 μm	Increased heat-affected zone compared to 9.3 μm wavelength of approximately 75 μm .	This configuration results in an increased heat-affected zone along the processed path when compared to the 9.3 μm configuration.	

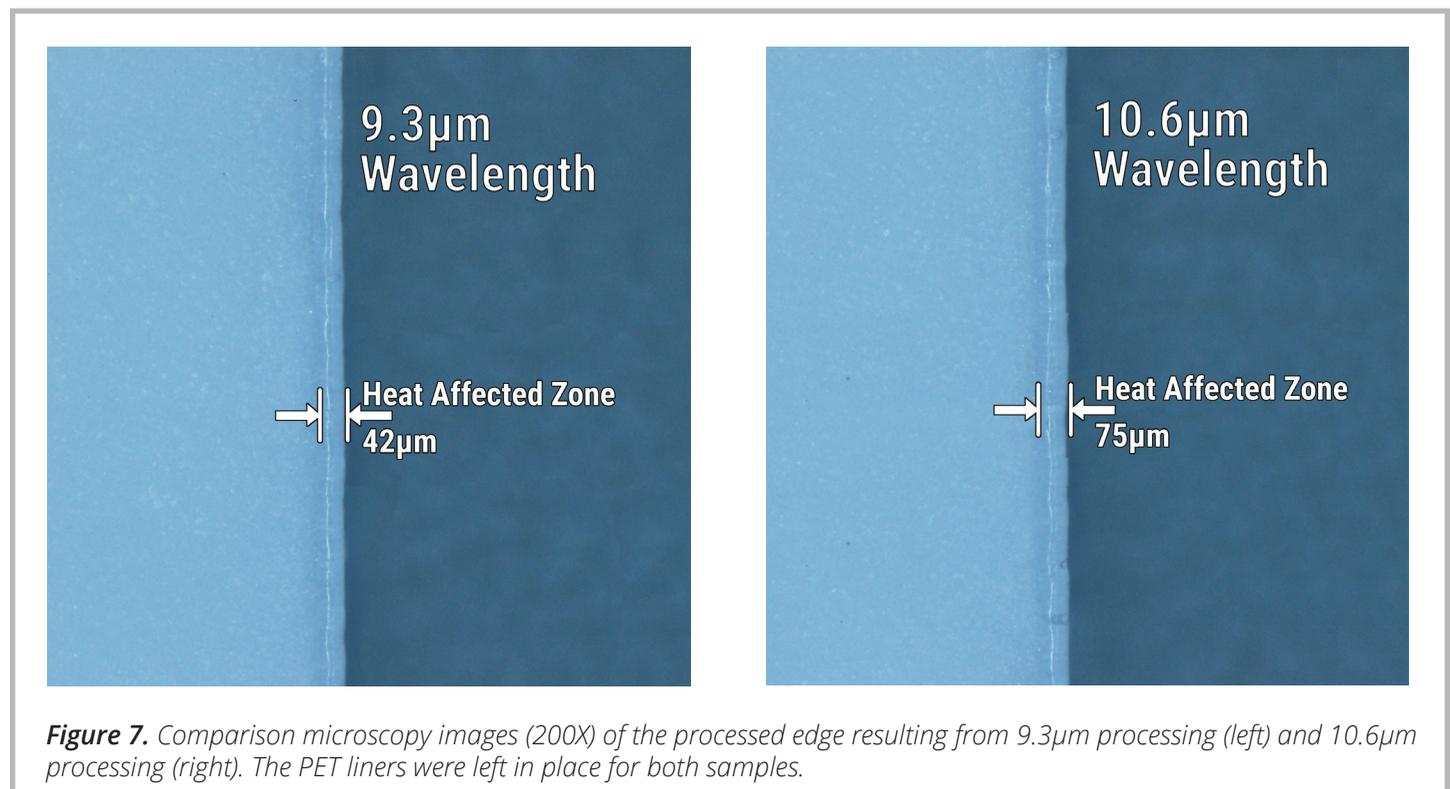

CONCLUSION

3M™ Thermally Conductive Adhesive Transfer Tape 8810 is very well suited for laser processing and was extensively tested to determine the most efficient processing configuration. Through this testing, it was determined that laser processing is viable with this material, and a 30 watt 9.3µm CO₂ laser source is the best configuration of wavelength and power for the processing of this material. The thermally conductive ceramic-filled acrylate layer and PET liners efficiently absorb the 9.3µm wavelength laser energy and, coupled with the peak power of the 30 watt laser source, produce a clean smooth processed edge that has minimal heat-affected zone and discoloration.

UNIVERSAL[®]
LASER SYSTEMS

3M

Universal Laser Systems, Inc.

www.ulsinc.com

Headquarters – Scottsdale, Arizona

800-859-7033 (480-483-1214)

moreinfo@ulsinc.com

3M is a trademark of 3M. All other trademarks are the property of their respective owners.

© 2021 Universal Laser Systems, Inc. All rights reserved. Universal Laser Systems logo and name are registered trademarks of Universal Laser Systems, Inc. All other company and product names are trademarks or registered trademarks of their respective companies.